

Comparison of the elastic modulus among three dentin adhesives before and after thermocycling

Juhea Chang¹, In Bog Lee¹, Byeong Hoon Cho¹, Hae-Young Kim², Ho Hyun Son^{1*}

¹*Department of Conservative Dentistry and Dental Research Institute, School of Dentistry, Seoul National University, Seoul, South Korea*

²*Craniomaxillofacial Life Science 21 and Dental Research Institute, School of Dentistry, Seoul National University, Seoul, South Korea*

ABSTRACT

The purpose of this study was to determine the effects on the elastic moduli of the adhesive and the hybrid layer from thermocycling. Twenty one human molars were used to create flat dentin surfaces. Each specimen was bonded with a light-cured composite using one of three commercial adhesives (OptiBond FL [OP], Clearfil SE Bond [CL], and Xeno III [XE]). These were sectioned into two halves and subsequently cut to yield 2-mm thickness specimens; one specimen for immediate bonding test without thermocycling and the other subjected to 10,000 times of thermocycling. Nanoindentation test was performed to measure the modulus of elasticity of the adhesive and the hybrid layer, respectively, using an atomic force microscope. After thermocycling, XE showed a significant decrease of the modulus in the adhesive layer ($p < 0.05$). Adhesives containing hydrophilic monomers are prone to hydrolytic degradation. It may result in the reduced modulus of elasticity, which leads to the mechanically weakened bonding interface. (J Kor Acad Cons Dent 33(1):45-53, 2008)

Key words : Adhesive layer, hybrid layer, hydrophilic monomer, modulus of elasticity, nanoindentation, thermocycling

- Received 2007.12.3., revised 2008.1.6., accepted 2008.1.9.-

I . INTRODUCTION

Recently tooth colored composite restorative materials are substituting enamel and dentin not only for the esthetic aspects but also mechanical properties, however, long-term serviceability is not yet guaranteed¹⁻³. Current dentin adhesives

avored user-friendliness and have been simplified into reduced-step systems. The inclusion of relatively high concentrations of acidic monomers and water, to permit ionization of those monomers and solution of calcium and phosphate, makes these polymers very hydrophilic. This hydrophilic nature of the adhesives rendered the resultant layer absorbing water over time, thereby decreasing stiffness⁴. During the service in the oral environment, water sorption within the adhesive interface may adversely affect stress distribution across the bonded interface and provide a weak link across the bonded complex⁴⁻⁶. A recent study correlated water sorption and the elastic modulus

* Corresponding Author: Ho Hyun Son

Department of Conservative Dentistry and Dental Research Institute, School of Dentistry, Seoul National Univ. 275-1 Yeongeon-dong, Jongno-gu Seoul, 110-749, Korea
Tel: 82-2-2072-2652 Fax: 82-2-2072-3859
E-mail: hhsn@snu.ac.kr

of dentin adhesives, using disc-shaped cured specimens and showed that water stored adhesives exhibited time-dependent decreases in modulus⁴). It was anticipated that lowered stiffness of adhesive layer coupling composite to dentin would result in poor load transfer across the interface, leading to joint failure.

Dentin has a localized structural divergence in location-specific tubular orientation, and there are difficulties in performing mechanical tests on small dentin specimens⁷). Recently, advances in nanoindentation technique made it possible to sample material properties with small applied loads and fine spatial resolutions⁸). It has been shown the accurate positioning capability of nanoindenter over the hybrid layer to yield hardness and elastic modulus from computerized measurements^{9,10}). This study compared the modulus of elasticity of the bonded interfaces produced with three commercial dentin adhesives (three-step etch and rinse, two-step self etch, and one-step self etch system) using a nanoindentation technique. It also aimed to determine whether any change in that property would be induced by thermo-cycling, and the change would be different among three commercial dentin adhesives.

II. MATERIALS AND METHODS

Specimen Preparation

Twenty one freshly extracted human molars (extracted before less than 2 wks) stored in 5% chloramines-T solution were used. Flat dentin surfaces were produced using a low speed diamond saw (Isomet, Buehler Ltd., Lake Bluff, IL, USA). The exposed dentin was abraded with #500 silicon carbide papers to create a clinically relevant smear layer. The twenty one dentin substrates were randomly divided into three adhesive groups; OptiBond FL [OP], Clearfil SE Bond [CL], and Xeno III [XE] (Table 1) and bonded with one of the adhesives following the manufacturer's directions. A commercial composite (Premisa, Kerr, USA) was applied to form a core 1-mm in thickness and light-cured in the same

condition (Figure 1). After storage in distilled water at 4°C for 6 days, each tooth was sectioned into halves occluso-gingivally perpendicular to the adhesive interface along its midpoint with a diamond saw. One half of a tooth was additionally sectioned from the midline to make a slab with 2-mm thickness. The slab was polished using silicon carbide paper with grit size up to 1200. Final polishing was performed with 6 μm to 0.25 μm diamond paste. The polished specimens were stored in distilled water at 4°C until nanoindentation testing. The other half of the tooth was thermocycled (5 - 55°C; dwell time 30 s; transfer time 5 s) for 10,000 cycles. After thermo-cycling, each tooth was sectioned and polished in the same way to yield a similar 2-mm slab to determine the effect from the thermocycling process.

Nanoindentation test

The indentation experiments were performed using a nano-based indentation system (Nano indenter XP, MTS Nano instruments, Oak Ridge, TN, USA). A load up to 20 mN was applied using a Berkovich diamond indenter with a calibrated area function at a rate of 0.5 mN/s. Indentations were made at 6 points in the middle of the adhesive and hybrid layer, respectively. Modified atomic force microscope (AFM) was used for an adequate location of the indenter with the 10 μm interval to avoid corruption of the examination surface. Following the Oliver-Pharr methodology, indenter force load and the depth of penetration into the specimen were continuously monitored, resulting in load-displacement curves to measure the elastic modulus¹¹⁻¹³). The following equation was used to calculate the effective indentation elastic modulus (E_r).

$$H = \frac{P_{max}}{A_c} \quad (1)$$

Where H is the hardness, P_{max} is the peak indentation load, and A_c is the projected contact area. The reduced elastic modulus is derived as follows:

$$E_r = \frac{\sqrt{\pi}}{2\sqrt{A_c}} S, \quad (2)$$

Where S , the contact stiffness is the initial slope of the unloading curve on the load-depth curve (Figure 2). For a non-rigid indenter that contacts the sample surface, the reduced elastic modulus can be described as:

$$\frac{1}{E_r} = \frac{(1 - \nu^2)}{E} + \frac{(1 - \nu_i^2)}{E_i}, \quad (3)$$

Where E and ν are the elastic modulus and Poisson's ratio of the specimen (0.2), respectively, and where i , as in E_i and ν_i , refers to the indenter material.

After nanoindentation test, specimens were dried in a desiccator for 5 days and subsequently gold-sputtered for microscopic observations. Field emission electron microscopy (FE-SEM) (S-4700, Hitachi, Pleasanton, CA, USA) was used to confirm the placement of the indentations.

Statistical analysis

An exploratory performance of a general linear model (GLM) revealed the significant inter-specimen differences ($p = 0.0134$). Mixed-level repeated analysis of variance (ANOVA) and Mixed-level repeated measures analysis of covariance (ANCOVA) were selected to compare the moduli of the three dentin adhesives at the immediate bonding and at the thermocycled stage, respectively, under consideration of six correlated measurements from the same specimen and differences among specimens. Modulus differences between the two conditions were separately compared using paired t-test. Mixed Procedure of statistical package SAS version 9.13 (SAS Institute, Cary, NC, USA) was used for analysis. A significance level of 0.05 was applied to identify statistically significant differences.

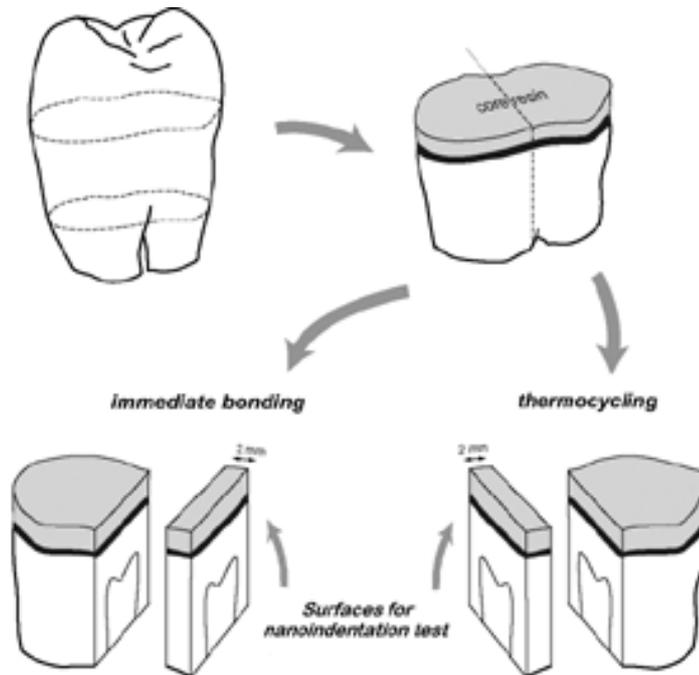


Figure 1. Schematic of specimen preparation. Two adjacent 2-mm sections were used for nanoindentation before and after thermocycling.

Table 1. Materials used in this study

Product	Component (Batch No)	Composition	Application
OptiBond FL (Kerr, Orange,CA, USA)	Prime (445404)	ethanol, Alkyl dimethacrylate, water	Etch for 15 s with 37.5% phosphoric acid (Kerr gel Etchant). Rinse for 15 s. Apply Prime and rub for 15 s. Dry for 5 s. Apply Adhesive in a uniform thin layer. Light cure for 30 s.
	Adhesive (446360)	Methcarylate ester monomers, Triethylene Glycol Dimethacrylate, Ytterbium Trifluoride, mineral fillers, initiators and stabilizers	
Clearfil SE (Kuraray, Osaka, Japan)	Self-Etch Primer (00568B)	HEMA, 10-MDP, hydrophilic DMA, CQ, water, toludine	Apply Primer and leave it in place for 20 s. Evaporate the volatile ingredients with air. Apply bonding agent. Light cure for 10 s.
	Adhesive (00808A)	Silanated silica, Bis-GMA, HEMA, hydrophobic DMA, 10-MDP, CQ, toludine	
Xeno III (Dentsply, Detrey, Konstanz, Germany)	Self-Etch Primer & Adhesive (Liquid A (Liquid A 0601002833, Liquid B 0601002832)	Liquid A: HEMA, water, EthanolUrethane dimethacrylate, BHT, silicon dioxide	Dispense equal amounts of Liquid A and Liquid B and mix it thoroughly for 5 s. Apply mixed adhesive and leave it undisturbed for 20 s. Light cure for 10 s.
		Liquid B: Phosphoric acid modified polymethacrylate, Mono fluoro phophazene modified methacrylate, Urethane dimethacrylate, BHT, CQ, Ethyl-4-dimethylaminobenzoate	

Bis-GMA = Bis-phenol-A-bis-(2-hydroxy-3-methacryloxypropyl)ether; BHT = Butylated hydroxyl toluene; CQ = 1,7,7-Trimethylbicyclo-[2,2,1]-hepta-2,3-dione; DMA = Dimethacrylate; HEMA = 2-Hydroxyethylmethacrylate; 10-MDP = 10-methacryloyloxydecyl dihydrogen phosphate

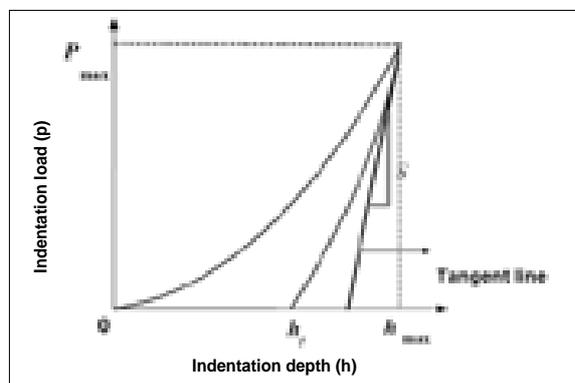


Figure 2. Schematic of load-depth curve in nanoindentation.

III . RESULTS

The mean values and standard deviations of elastic modulus obtained by nanoindentation are shown in Table 2. On the adhesive layer, OP showed the significantly higher modulus of elasticity than XE and CL at the immediate bonding, ($p = 0.0094$) and at the thermocycled stage ($p = 0.0061$). After thermocycling, the elastic modulus of OP rarely changed, while CL decreased slightly, though not in a statistically significant manner. On the other hand, XE significantly dropped

by 3.6 GPa ($p = 0.0246$). For the hybrid layer, the elastic modulus of OP was the highest, followed by CL and XE. After thermocycling each group had the same tendency to a decrease, not in a statistically significant way. FE-SEM micrographs illustrating the indentation geometry and the accurate positioning capacity are presented in Figure 3.

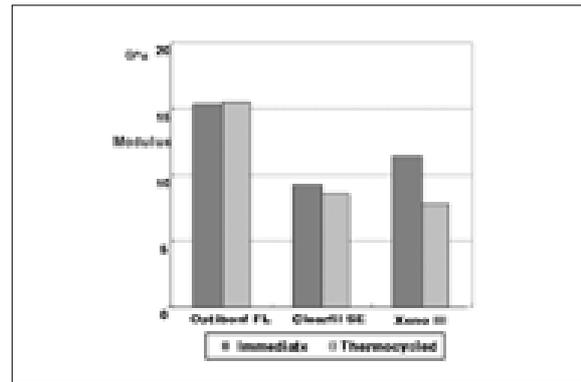


Figure 3. Comparative mean elastic moduli of three adhesive systems on the adhesive layer at the immediate bonding and the thermocycled stage.

Table 2. Modulus of elasticity* of bonding interface at the immediate bonding and the thermocycled stage (GPa)

Layer	State [†]	Type of Adhesives [‡]			p-value
		OptiBond FL [OP]	Clearfill SE [CL]	Xeno III [XE]	
Adhesive	immediate	15.3 (7.7) ^a	9.2 (3.8) ^b	11.4 (3.4) ^{Ab}	0.0094
	thermocycling	15.5 (16.1) ^a	8.5 (2.2) ^b	7.8 (5.3) ^{Bb}	0.0061
	p-value	0.8878	0.5942	0.0246	
Hybrid	immediate	20.1 (9.0)	16.7 (5.9)	15.5 (5.0)	0.1595
	thermocycling	18.3 (12.4)	12.3 (9.8)	13.0 (7.1)	0.1149
	p-value	0.5397	0.0940	0.1648	

Means and standard deviations in parentheses. Data with the different letters are significantly different at the 0.05 significance level. Upper cases indicate the comparisons of two time points and lower cases indicate the comparison of the three types of adhesives.

* Relative modulus was measured on 6 locations of each specimen, and 7 specimens per each type of adhesive were allocated.

† Modulus values after thermocycling were compared under adjusting for values at the immediate bonding state.

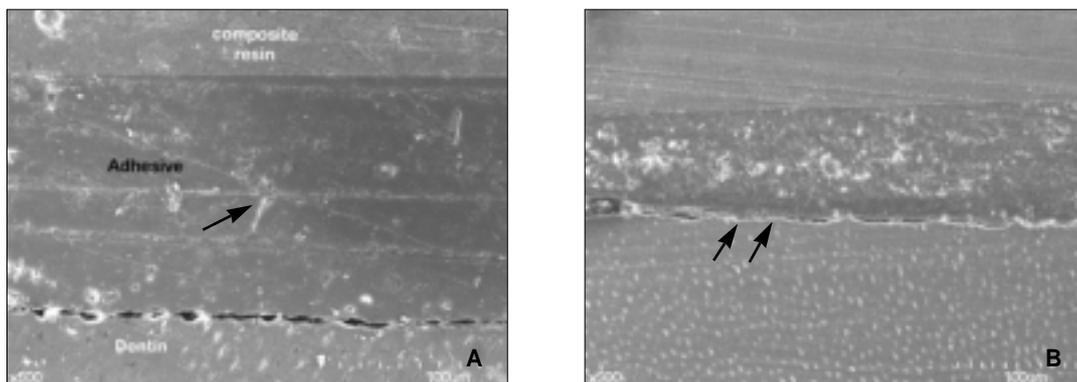


Figure 4. FE-SEM micrographs of bonded interface. Arrows indicate the representative indentations on the adhesive layer of OP (A) and the hybrid layer of CL (B) after thermocycling. Cracks propagated from the contact point were exhibited on the indentation surface. Some indentation marks seemed to be elastically recovered after unloading without leaving permanent defects.

IV. DISCUSSION

There have been many attempts to verify the unstable bonded interface resulting from hydrolytic degradation. Water permeability in the hydrophilic adhesive interface has been well documented using various microscopic methodologies¹⁴⁻¹⁷. This hydrolysis susceptible area was clearly depicted in micrographs and weak junctions were often confirmed by bond strength tests, which determine fracture position^{1,17-20}. Our study was designed to verify the mechanical properties of each component in the bonding interface by measuring the elastic modulus. Water sorption of polymers is known to make its structure more plasticized and loosely linked monomer particles can be dissolved in the hydrolytic condition. Adhesive materials incorporate hydrophilic primer within their systems and have demonstrated higher water sorption and solubility than the composite resin^{21,22}. It was readily expected that simplified-step adhesive systems would allow higher water sorption and a higher degree of plasticization, resulting in greater deterioration of mechanical property. Previous *in vitro* experiments tended to standardize specimen fabrication using the polymerized sticks of the adhesive-primer mixture and measured their solubility and elastic modulus²²⁻²⁴. However, this method is far-removed from the clinical environment, where the bonding surface is rubbed with a primer dampened brush and dried with a light air stream, and additionally coated with adhesive. Moreover, it does not incorporate the hybrid layer, the resin impregnated organic substance, which is also subjected to the hydrolytic degradation. Our study tried to reproduce the actual clinical circumstance, following the manufacturer's direction in the bonding procedure. Another attempt given in the study is to minimize the divergence of dentin substrate by using the same tooth in comparison between before and after thermocycling. Two mirror-image surfaces were compared, having one surface represent the immediate bonding stage and the other the thermocycled one. A comparison of the mechanical property between these two

adjacent interfaces was expected to be more relevant, because the two counterpart surfaces contain the similar histological features.

At the state of immediate bonding, the elastic modulus of the hybrid layer was higher than of the adhesive layer in all groups, as in previous studies^{25,26}. This zone, in which resinous materials were penetrated into a partially decalcified dentin, still remained a rather stiff resin-dentin interdiffusion area, compared to the pure adhesive layer. After thermocycling, the differences between two layers existed (Table 2). OP which is relatively heavily loaded with fillers (52%) had a significantly higher elastic modulus in the adhesive layer than the other groups. With this traditional three-step etch and rinse system, the thick hydrophobic layer excluded the hydrophilic primed dentin and sustained thermocycling without signs of deterioration (Table 2). CL also adopted the separate bottle of hydrophobic adhesive. Its different filler system might contribute to the slight decrease in the modulus after thermocycling, but not significantly. XE showed a significantly great decrease after thermocycling. The hydrophilic interface produced by this all-in-one system might have been more prone to hydrolysis. After water entered the polymer matrix, the microstructure of adhesive layer was possibly changed due to progressive degradation through pore formation²². Residual monomers, oligomers and degradation products might have been released via these pores, impairing the structural rigidity. As for the hybrid layer, this tendency was similar to that shown in the overlying adhesive layer. OP showed the higher modulus, representing a stiffer backbone of polymer within the collagen network. However, even OP showed a decrease in modulus after thermocycling, although not significantly. There may be the assumption given that less complete polymerization within the collagen network accomplished and the unpolymerized monomers have been leached during thermodynamic process²². As water has been known to be one of the major causes for collagen degradation, disorganization of collagen fibrils may have played an additional role in the change

in bonding stability¹⁾.

Nanoindentation technique allowed us to determine surface mechanical properties from load-displacement indentation data. In spite of the minute indent contact area, a filler embedded matrix structure might not provide the uniform surface for examination and this anisotropic nature could account for the large standard deviation observed in this study²⁷⁾. This also explained why other nanoindentation studies have allowed multiple measurements and put mean values into data processing²⁶⁻²⁹⁾. Interspecimen differences were statistically significant ($p < .00128$), while differences were not significant among measurements within the same specimen. This suggested that consideration of the individual differences among specimens was inevitable and at the same time supported the protocol used here to minimize the structural divergence of dentin substrate. However, considering that the peripheral composite-enamel bond was shown to reduce the degradation rate in resin-dentin interface^{30,31)}, the results of our study may be exaggerated, because the bonding surfaces were directly exposed to hydrothermal environment. Another drawback in this study was that thermocycling process may not reflect degradation within the mouth, although 10,000 times of cycles was suggested to represent one service year³²⁾. Therefore, the limitations imposed on these *in vitro* experimental conditions needs to be considered.

V. CONCLUSION

In this study, three different versions (three-step, two-step, and all-in-one system) of commercial adhesive resins were compared to determine the effects of thermocycling on the elastic modulus of the adhesive or the hybrid layer. Only XE group, an all-in-one type adhesive had a significantly decreased modulus in the adhesive layer after 10,000 thermocycles. When adhesives contain more hydrophilic monomers, they may be more prone to hydrolytic degradation, resulting in a mechanically weakened bonding interface. Adhesive systems including separate hydrophobic

adhesive with fillers may be more capable of sustaining the hydrous conditions of the oral cavity. Based on the result of this study, some all-in-one self-etch system may be more affected by the hydrolytic degradation over time. It seems that clinicians need to be considerate in selecting materials and procedures, which is predicative of a clinical longevity of bonded restorations.

Acknowledgements:

The authors give special thanks to Ju-Young Kim and Seung-Kyun Kang in Nano-Mechanics & System Characterization Laboratory, School of Materials Science and Engineering, Seoul National University, for conducting the nanoindentation tests.

REFERENCES

1. Hashimoto M, Ohno H, Sano H, Kaga M, Oguchi H. *In vitro* degradation of resin-dentin bonds analyzed by microtensile bond test, scanning and transmission electron microscopy. *Biomaterials* 24:3795-3803, 2003.
2. Breschi L, Mazzoni A, Ruggeri A, Cadenaro M, Di Lenarda R, De Stefano Dorigo E. Dental adhesion review: Aging and stability of the bonded interface. *Dent Mater* (in press) 16:16, 2007.
3. Dijken JW, Sunnegardh-Gronberg K, Lindberg A. Clinical long-term retention of etch-and-rinse and self-etch adhesive systems in non-carious cervical lesions A 13 years evaluation. *Dent Mater* 23:1101-1107, 2007.
4. Ito S, Hashimoto M, Wadgaonkar B, Svizero N, Carvalho RM, Yiu C et al. Effects of resin hydrophilicity on water sorption and changes in modulus of elasticity. *Biomaterials* 26:6449-6459, 2005.
5. De Munck J, Van Meerbeek B, Yoshida Y, Inoue S, Vargas M, Suzuki K et al. Four-year water degradation of total-etch adhesives bonded to dentin. *J Dent Res* 82:136-140, 2003.
6. Carrilho MR, Tay FR, Pashley DH, Tjaderhane L, Carvalho RM. Mechanical stability of resin-dentin bond components. *Dent Mater* 21:232-241, 2005.
7. Angker L, Nockolds C, Swain MV, Kilpatrick N. Correlating the mechanical properties to the mineral content of carious dentine—a comparative study using an ultra-micro indentation system (UMIS) and SEM-BSE signals. *Arch Oral Biol* 49:369-378, 2004.
8. Marshall GW, Jr., Balooch M, Gallagher RR, Gansky SA, Marshall SJ. Mechanical properties of the dentinoenamel junction: AFM studies of nanohardness, elastic modulus, and fracture. *J Biomed Mater Res* 54:87-95, 2001.
9. Oliveira SS, Marshall SJ, Habelitz S, Gansky SA, Wilson RS, Marshall GW, Jr. The effect of a self-etching primer on the continuous demineralization of dentin. *Eur J Oral Sci* 112:376-383, 2004.

10. Inoue G, Tsuchiya S, Nikaido T, Foxton RM, Tagami J. Morphological and mechanical characterization of the acid-base resistant zone at the adhesive-dentin interface of intact and caries-affected dentin. *Oper Dent* 31:466-472, 2006.
11. Oliver WC PG. An improved technique for determining hardness and elastic modulus using load and displacement sensing indentation experiments. *J Mater Res* 7:1564-1583, 1992.
12. Ge J, Cui FZ, Wang XM, Feng HL. Property variations in the prism and the organic sheath within enamel by nanoindentation. *Biomaterials* 26:3333-3339, 2005.
13. Doerner MF NW. A method for interpreting the data from depth-sensing indentation instruments 1:601-609, 1986.
14. Donmez N, Belli S, Pashley DH, Tay FR. Ultrastructural correlates of *in vivo/in vitro* bond degradation in self-etch adhesives. *J Dent Res* 84:355-359, 2005.
15. Reis AF, Giannini M, Pereira PN. Long-term TEM analysis of the nanoleakage patterns in resin-dentin interfaces produced by different bonding strategies. *Dent Mater* 23(9):1164-1172, 2007.
16. Yuan Y, Shimada Y, Ichinose S, Tagami J. Qualitative analysis of adhesive interface nanoleakage using FE-SEM/EDS. *Dent Mater* 23(5):561-569, 2007.
17. Toledano M, Osorio R, Albaladejo A, Aguilera FS, Osorio E. Differential effect of *in vitro* degradation on resin-dentin bonds produced by self-etch versus total-etch adhesives. *J Biomed Mater Res A* 77:128-135, 2006.
18. Koshiro K, Inoue S, Tanaka T, Koase K, Fujita M, Hashimoto M et al. *In vivo* degradation of resin-dentin bonds produced by a self-etch vs. a total-etch adhesive system. *Eur J Oral Sci* 112:368-375, 2004.
19. Tay FR, Suh BI, Pashley DH, Prati C, Chuang SF, Li F. Factors contributing to the incompatibility between simplified-step adhesives and self-cured or dual-cured composites. Part II. Single-bottle, total-etch adhesive. *J Adhes Dent* 5:91-105, 2003.
20. Hashimoto M, Ohno H, Sano H, Tay FR, Kaga M, Kudou Y et al. Micromorphological changes in resin-dentin bonds after 1 year of water storage. *J Biomed Mater Res* 63:306-311, 2002.
21. Burrow MF, Inokoshi S, Tagami J. Water sorption of several bonding resins. *Am J Dent* 12:295-298, 1999.
22. Reis AF, Giannini M, Pereira PN. Influence of water-storage time on the sorption and solubility behavior of current adhesives and primer/adhesive mixtures. *Oper Dent* 32:53-59, 2007.
23. Malacarne J, Carvalho RM, de Goes MF, Svizero N, Pashley DH, Tay FR et al. Water sorption/solubility of dental adhesive resins. *Dent Mater* 22:973-980, 2006.
24. Hosaka K, Tagami J, Nishitani Y, Yoshiyama M, Carrilho M, Tay FR et al. Effect of wet vs. dry testing on the mechanical properties of hydrophilic self-etching primer polymers. *Eur J Oral Sci* 115:239-245, 2007.
25. Van Meerbeek B, Willems G, Celis JP, Roos JR, Braem M, Lambrechts P et al. Assessment by nano-indentation of the hardness and elasticity of the resin-dentin bonding area. *J Dent Res* 72:1434-1442, 1993.
26. Hosoya Y, Tay FR. Hardness, elasticity, and ultrastructure of bonded sound and caries-affected primary tooth dentin. *J Biomed Mater Res B Appl Biomater* 81:135-141, 2007.
27. Drummond JL. Nanoindentation of dental composites. *J Biomed Mater Res B Appl Biomater* 78:27-34, 2006.
28. Xu HH, Smith DT, Jahanmir S, Romberg E, Kelly JR, Thompson VP et al. Indentation damage and mechanical properties of human enamel and dentin. *J Dent Res* 77:472-480, 1998.
29. Senawongse P, Harnirattisai C, Otsuki M, Tagami J. Effect of LED light-curing time for the adhesive resin on the modulus of elasticity. *Am J Dent* 20:139-141, 2007.
30. Reis AF, Giannini M, Pereira PN. Effects of a peripheral enamel bond on the long-term effectiveness of dentin bonding agents exposed to water *in vitro*. *J Biomed Mater Res B Appl Biomater* (in press) 6:6, 2007.
31. Toledano M, Osorio R, Osorio E, Aguilera FS, Yamauti M, Pashley DH et al. Durability of resin-dentin bonds: effects of direct/indirect exposure and storage media. *Dent Mater* 23:885-892, 2007.
32. Gale MS, Darvell BW. Thermal cycling procedures for laboratory testing of dental restorations. *J Dent* 27:89-99, 1999.

국문초록

열시효 처리에 따른 상아질 접착 계면의 탄성계수의 변화 비교

장주혜¹ · 이인복¹ · 조병훈¹ · 김혜영² · 손호현^{1*}

¹서울대학교 치의학전문대학원, ²서울대학교 치의학생명과학사업단

본 연구는 현재 시판 되고 있는 여러 개의 상아질 접착제를 임상 술식에서와 같은 방법으로 사용한 후 열 시효처리를 통해 노화 과정을 재현한 다음 접착 계면의 탄성계수를 측정함으로써 가수분해에 따른 물성변화를 관찰 비교하고자 했다.

발거 한 지 2 주일 이내인 영구 대구치 21 개의 상아질 표면이 노출되도록 삭제하였다. 각각 7개의 치아에 시판되고 있는 3가지 상아질 접착제 (OptiBond FL, Clearfil SE, Xeno III)를 적용한 뒤 광중합 복합 레진 (Premisa, Kerr, Orange, CA, USA) 를 1 mm 두께로 쌓아 올렸다. 각 치아를 이등분하여 절반 시편은 100,000 회의 열 시효 처리를 가하도록 했다. Nanoindentation test를 통하여 각 시편의 adhesive layer와 hybrid layer의 탄성계수를 측정, 비교하였다. 열시효 처리 후 Xeno III군의 탄성계수가 통계학적으로 유의할 만한 감소를 보였다 ($p < 0.05$). Hydrophilic monomer를 많이 함유한 one-step self-etch adhesive system은 다른 제품에 비해 가수분해에 취약하여 이에 따른 물성 변화를 보이는 것으로 추정되며, 궁극적으로 수복물의 내구성에 영향을 미칠 것으로 여겨진다.

주요어: 탄성계수, Nanoindentation, Adhesive layer, Hybrid layer, 열시효 처리, Hydrophilic monomer