

The effect of MTAD on the apical leakage of obturated root canals: an electrochemical study

Dong-Sung Park

Department of Conservative Dentistry, Samsung Medical Center, Sungkyunkwan University School of Medicine

ABSTRACT

The purpose of this study was to evaluate the effect of newly developed endodontic root canal cleanser (MTAD) on the apical leakage of obturated root canal using an electrochemical method.

Canals of 60 extracted single-rooted human teeth were prepared by using a crown-down technique with rotary nickel-titanium files. In Group 1 (positive control group) and 2 (negative control group), 5.25% NaOCl was used as a canal irrigant and no canal wall treatment was done. In group 3, only 5.25% NaOCl were used as canal irrigant, canal wall treatment and final rinse. In group 4, specimens were irrigated with 5.25% NaOCl, treated with 5 ml of 17% EDTA for 5 minutes and final rinsed with 5.25% NaOCl. Specimens of group 5 were irrigated with 1.3% NaOCl and treated with 5 ml of MTAD for 5 minutes. All root canals are dried with paper points and obturated with gutta-percha and AH plus as a sealer using a continuous wave of condensation technique except in the group 1. The electrical resistance between the standard and experimental electrodes in canals was measured over a period of 10 days. Rising of apical leakage with time was observed for all the groups. Group 4 and 5 showed lower apical leakage than group 3 but differences between the group 3, 4 and 5 were no statistical significance at any measurement time. [J Kor Acad Cons Dent 31(2):119-124, 2006]

Key words : Smear layer, Electrochemical method, Apical leakage, Root canal irrigant

- Received 2005.11.1., revised 2006.2.6., accepted 2006.2.16. -

I . INTRODUCTION

The smear layer was first described by McComb in a scanning electron microscope (SEM) study¹⁾. The smear layer consists of organic and inorganic substances, including fragments of odontoblastic

processes, dentinal shaving, microorganisms, and necrotic materials. Presence of this smear layer prevents penetration of intracanal medication into the irregularities of the root canal system and the dentinal tubules and also prevents complete adaptation of obturation materials to the prepared root canal surfaces²⁾. Its removal calls for a combination of irrigating solutions as, presently, one solution cannot dissolve both organic and inorganic debris³⁾. Upon the completion of instrumentation, a high volume final flush with ethylene diamine tetra-acetic acid (EDTA) solution followed by NaOCl was found to be most effective in removing

* Corresponding Author: **Dong-Sung Park**

Dept. of Conservative Dentistry, Samsung Medical Center,
Sungkyunkwan University School of Medicine
50, Ilwon-Dong, Kangnam-Ku, Seoul, Korea, 135-710
Tel: 82-2-3410-2429 Fax: 82-2-3410-0038
E-mail: dsparkh@smc.samsung.co.kr

superficial debris and smear layer from root canal walls⁴⁾.

Studies^{5,6)} have shown a significant increase in adhesive strength and resistance to microleakage of AH26 sealer when the smear layer was removed. Gettleman *et al.*⁵⁾ reported that they did not find any changes in adhesive strengths when Sultan and Sealapex sealers were evaluated with or without the smear layer intact. Several investigators⁶⁻¹²⁾ have shown less dye leakage after removal of the smear layer, with various obturation techniques and root canal sealers.

Other investigators have reported that the removal of the smear layer did not have any significant effect on microleakage of root canals using various sealers and obturation techniques¹³⁻¹⁶⁾.

In contrast to these findings Timpawat *et al.*¹⁷⁻¹⁸⁾ have reported that removal of the smear layer have adverse effects on microleakage of filled root canals.

A mixture of a tetracycline isomer, an acid, and detergent (MTAD) is known as an effective solution for the removal of the smear layer and does not significantly change the structure of the dentinal tubules when canals are irrigated with sodium hypochlorite and followed with a final rinse of MTAD¹⁹⁾.

The purpose of this study was to evaluate the effect of newly developed endodontic root canal cleanser on the apical leakage of obturated root canal using an electrochemical method.

II. MATERIALS AND METHODS

Sixty non-carious human mature extracted maxillary or mandibular anterior teeth or premolars with a single root canal and a closed apex were distributed randomly into five groups of 12 teeth each. After preparing a conventional access preparation for each tooth, a K-type file (size 10 or 15) was used to determine the working length by penetrating the apical foramen and pulling back into the clinical apical foramen. Whilst cleaning and shaping up to a size 40 master apical file with a crown-down technique and Rotary

0.04 and 0.06 Taper Profile (Profile, Dentsply-Maillefer, Switzerland), the root canals were irrigated with 2 ml of 5.25% or 1.3% NaOCl in each group between each file size. 17% EDTA (REDTA, Roth International Ltd, Chicago, USA), 5.25% NaOCl or MTAD were used as a canal wall treatment. A total of 10 ml of irrigant was used in each root canal. The irrigant was delivered with a 27 gauge plastic needle (Capillary Tips, Ultradent product Inc., South Jordan, USA) reaching to within 1-2 mm from the working length in each canal.

5.25% NaOCl was used as a canal irrigant in twelve teeth. After canal shaping and cleaning, root canals were obturated with only gutta-percha. These teeth were used as Group 1 (G1) or positive control group. In Group 2 (G2) or negative control group, root canals were also irrigated with 5.25% NaOCl and obturated with gutta-percha and AH plus. After that, apical portion of the roots was sealed with sticky wax. In Group 3 (G3), only 5.25% NaOCl was used as a canal irrigant, canal wall treatment and final rinse. In Group 4 (G4), specimens were irrigated with 5.25% NaOCl, treated with 5 ml of 17% EDTA for 5 minutes and final rinsed with 5.25% NaOCl. Specimens of Group 5 (G5) were irrigated with 1.3% NaOCl and treated with 5 ml of MTAD for 5 minutes. Summary of the use of canal irrigation solution was presented in table 1.

All root canals were dried with paper points and obturated with gutta-percha and AH plus (AH plus, Dentsply, York, USA) as a sealer using a continuous wave of condensation technique except in the group 1. All roots were stored at 100% humidity for 1 day.

For all the specimens, the coronal gutta-percha was removed with #2 or #3 Gate Glidden burs and the apical 8 mm of root canal filling was left. This was confirmed radiographically. Copper wire was inserted into the canals as experimental electrodes in contact with the remaining gutta-percha. They were secured in place with sticky wax. The roots were coated with a triple layer of nail-polish except apical 8 mm in group 1, 3, 4 and 5. In the group 2, after root canal obturation, apical

portion of root was covered with sticky wax and nail varnish was coated over all tooth surfaces including the sticky wax three times.

All the specimens were placed in the bottles. The copper wire as an experimental electrode was fixed in the canal and extended to the outside of the bottle cap. The stainless steel wire as a standard electrode was located at the center of the bottle as like in Park *et al's* study²⁰⁾ (Figure 1). A 0.9% NaCl solution as an electrolyte was placed in the bottle until the apical 8 mm of the roots was covered.

The electrical resistance between the standard and experimental electrode was measured over a period of 10 days using a multitester (Radio-

Shack, Digital Multimeter, USA). On the first days, the electric resistance was measured at baseline and then at 0.5, 1, 2, 4, 6, 9 and 12 hour. The resistance was then measured at 24 hour and then once a day for 10 days.

A Kruskal-Wallis one-way analysis method was used along with the Student-Newman-Keuls method for mutiple comparison procedures.

III . RESULTS

Increasing apical leakage with time was observed for all the groups.

Group 4 and 5 showed lower apical leakage than group 3 but there were no statistically significant

Table 1. Irrigating solutions and obturation materials used in control and experimental groups

Group	Specimen	Irrigation and rinsing agents	Obturation
Group 1 (positive control)	12	5.25% NaOCl	Gutta-percha only
Group 2 (negative control)	12	5.25% NaOCl	Gutta-percha, AH plus, and sticky wax
Group 3	12	5.25% NaOCl	Gutta-percha and AH plus
Group 4	12	5.25% NaOCl and treated with 5 ml of 17% EDTA for 5 minutes and final rinsed with 5.25% NaOCl	Gutta-percha and AH plus
Group 5	12	Canal irrigation with 1.3% NaOCl, treated with 5 ml of MTAD for 5 minutes	Gutta-percha and AH plus

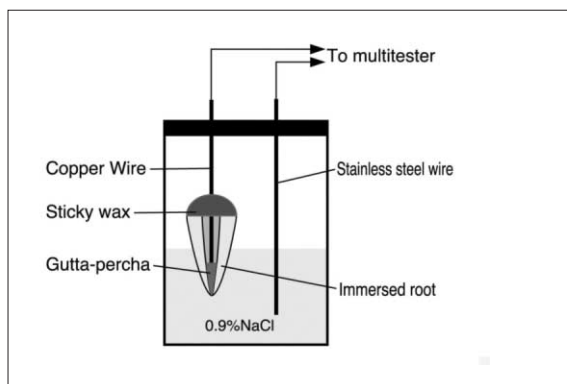


Figure 1. A schematic drawing of test system.

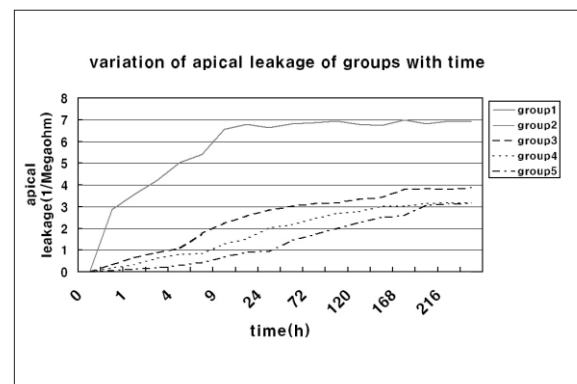


Figure 2. Variation of apical leakage of groups with time.

Table 1. Mean apical leakage ($M\Omega^{-1}$) and standard deviation of groups

hour	Group 1		Group 2		Group 3		Group 4		Group 5	
	Mean	S.D.	Mean	S.D.	Mean	S.D.	Mean	S.D.	Mean	S.D.
0	0	0	0	0	0	0	0	0	0	0
0.5	2.88	1.09	0	0	0.32	0.06	0.18	0.05	0.06	0.03
1	3.57	2.01	0	0	0.65	0.11	0.33	0.11	0.13	0.04
2	4.21	1.13	0	0	0.89	0.54	0.64	0.08	0.17	0.09
4	5.04	2.45	0	0	1.09	0.28	0.81	0.13	0.29	0.24
6	5.42	1.99	0	0	1.76	0.39	0.83	0.15	0.44	0.16
9	6.56	0.58	0	0	2.23	0.56	1.29	0.97	0.67	0.34
12	6.78	1.23	0	0	2.57	0.61	1.50	0.54	0.91	0.26
24	6.63	2.34	0	0	2.85	0.70	2.01	0.72	0.94	0.38
48	6.81	1.57	0	0	3.02	1.41	2.17	0.17	1.44	0.16
72	6.87	0.82	0	0	3.14	0.93	2.43	0.09	1.70	0.35
96	6.94	2.04	0	0	3.16	0.77	2.68	0.14	2.00	0.34
120	6.80	2.52	0	0	3.35	1.82	2.77	0.53	2.26	0.94
144	6.75	1.85	0	0	3.41	1.03	3.01	0.68	2.51	0.73
168	6.99	1.78	0	0	3.79	1.42	3.03	0.82	2.58	0.31
192	6.83	1.11	0	0	3.83	0.85	3.15	0.93	3.08	1.43
216	6.94	1.76	0	0	3.81	1.07	3.17	0.57	3.11	0.44
240	6.92	3.14	0	0	3.88	0.69	3.16	0.89	3.15	0.53

differences between the group 3, 4 and 5 at any measurement time.

The differences between the groups are outlined in Figure 2 and the detailed data are provided in Table 2.

IV. DISCUSSION

Kennedy *et al.*⁷⁾ reported that removal of smear layer reduced apical leakage when using chloroform-softened master cones with sealer and a lateral condensation technique. They described that several factors such as improved mechanical locking of sealer into patent tubules, better adhesion to cleaner canal walls, and greater canal wall sealing surface area might be responsible for this reduced apical leakage. In this study, the apical leakage of group 5 was lowest except group 2 (negative control group). Group 4 and 5 had less apical leakage than group 3. But differences between the group 3, 4 and 5 were not statistical-

ly significant. Based on the above results, the removal of smear layer was not thought to affect the apical leakage and MTAD may have better effect on the apical leakage than EDTA. In Karagoz-Kucukay's study¹¹⁾, comparison of the groups with smear layer present versus those with smear layer removed showed a highly significant difference, with the incidence of leakage reduced in the absence of the smear layer. In this study, there was no statistically significant difference between the group with smear layer and the groups without smear layer in the aspect of quantitative measurement.

Baumgartner *et al.*²¹⁾ evaluated the amount of superficial debris and the smear layer that remained on the canal wall following a combination of NaOCl and 50% citric acid. They showed that citric acid or a combination of NaOCl and citric acid irrespective of the order in which they were used was more effective than NaOCl alone to remove the smear layer from the surface of

instrumented canals. Because high concentrations of NaOCl are more toxic than diluted solutions and there are no significant differences between the ability of 1.3%, 2.6% and 5.25% as root canal irrigants and MTAD as a final rinse to remove the smear layer²², 1.3% NaOCl during instrumentation and MTAD as a final rinse was used to remove the smear layer in Group 5.

In this study, leakage analysis was done for 10 days. Delivanis *et al.*²³ have shown in an electrochemical study, that there was a very sharp increase in the penetration during the first 10 days. A possible reason for this increase may be that the materials set and become dimensionally stable because of their hygroscopic and physical characteristics. Various factors such as anatomical variations, preparation of teeth, sealers used, immersion times and methods of evaluating leakage may affect the results and may be the reason for the lack of correlation between similar studies.

Further studies are necessary to evaluate the long-term apical leakage change and the coronal leakage change.

REFERENCES

- McComb D, Smith DC. A preliminary scanning electron microscopic study of root canals after endodontic procedures. *J Endodon* 1(7):238-242, 1975.
- Torabinejad M, Handysides R, Khademi A, Bakland LK. Clinical implications of the smear layer in endodontics: a review. *Oral Surg Oral Med Oral Pathol Oral Radiol Endo* 94(6):658-666, 2002.
- Baumgartner JC, Mader CL. A scanning electron microscopic evaluation of four root canal irrigation regimens. *J Endodon* 13(4):147-157, 1987.
- Yamada RS, Armas A, Goldman M, Lin PS. A scanning electron microscopic comparison of a high volume flush with several irrigating solutions. Part 3. *J Endodon* 9(4):137-142, 1983.
- Gettleman BH, Messer HH, ElDeeb ME. Adhesion of sealer cements to dentin with and without the smear layer. *J Endodon* 17(1):15-20, 1991.
- Economides N, Liolios E, Kolokuris I, Beltes P. Long-term evaluation of the influence of smear layer removal on the sealing ability of different sealers. *J Endodon* 25(2):123-25, 1999.
- Kennedy WA, Walker WA, Gough RW. Smear layer removal effects on apical leakage. *J Endodon* 12(1):21-27, 1986.
- Cergneux M, Ciucchi B, Dietschi JM, Holz J. The influence of the smear layer on the sealing ability of canal obturation. *Int Endod J* 20(5):228-232, 1987.
- Vassiliadis L, Liolios E, Kouvas V, Economides N. Effect of smear layer on coronal microleakage. *Oral Surg Oral Med Oral Pathol Oral Radiol Endod* 82(3):315-320, 1996.
- Taylor JK, Jeanson BG, Lemon RR. Coronal leakage: Effects of smear layer, obturation technique, and sealer. *J Endodon* 23(8):508-512, 1997.
- Karagöz-Küçükay I, Bayirli G. An apical leakage study in the presence and absence of the smear layer. *Int Endod J* 27(2):87-93, 1994.
- Saunders WP, Saunders EM. The effect of smear layer upon the coronal leakage of gutta percha root filling and a glass ionomer sealer. *Int Endod J* 25(5):245-249, 1992.
- Evans JT, Simon JHS. Evaluation of the apical seal produced by injected thermoplasticized gutta-percha in the absence of smear layer and root canal sealer. *J Endodon* 12(3):101-107, 1986.
- Chailertvanitkul P, Saunders WP, Mackenzie D. The effect of smear layer on microbial coronal leakage of gutta-percha root fillings. *Int Endod J* 29(4):242-248, 1996.
- Saunders WP, Saunders EM. Influence of smear layer and the coronal leakage of thermafil and laterally condensed gutta-percha root fillings with a glass ionomer sealer. *J Endodon* 20(4):155-158, 1994.
- Madison S, Krell KV. Comparison of ethylenediamine tetracetic acid and sodium hypochlorite on the apical seal of endodontically treated teeth. *J Endodon* 10(10):499-503, 1984.
- Timpawat S, Sripanaratanakul S. Apical sealing ability of glass ionomer sealer with and without smear layer. *J Endodon* 24(5):343-345, 1998.
- Timpawat S, Vongsavan N, Messer HH. Effect of removal of the smear layer on apical microleakage. *J Endodon* 27(5):351-353, 2001.
- Torabinejad M, Khademi AA, Babagoli J, Cho Y, Johnson WB, Bozhilov K, Kim J, Shabahang S. A new solution for the removal of the smear layer. *J Endodon* 29(3):170-175, 2003.
- DS Park, HJ Lee, HM Yoo and TS Oh. Effect of Nd:YAG laser irradiation on the apical leakage of obturated root canals: an electrochemical study. *Int Endodon J*, 34(4):318-321, 2001.
- Baumgartner JC, Brown CM, Mader CL, Peters DD, Shulman JD. A scanning electron microscopic evaluation of root canal debridement using saline, sodium hypochlorite and citric acid. *J Endodon* 10(11):525-531, 1984.
- Torabinejad M, Cho Y, Khademi AA, Bakland LK, Shabahang S. The effect of various concentrations of sodium hypochlorite on the ability of MTAD to remove smear layer. *J Endodon* 29(4):233-239, 2003.
- Delivanis PD, Chapman KA. Comparison and reliability of techniques for measuring leakage and marginal penetrations. *Oral Surg* 53(4):410-416, 1982.

국문초록

MTAD의 치근단 누출에 미치는 영향에 대한 전기화학적 연구

박 동 성

성균관대학교 의과대학 삼성서울병원 치과보존과

본 연구는 새로이 개발된 근관세정제 (MTAD)가 근관 충전이 이루어지고 난 치근단 누출에 미치는 영향을 평가해 보고자 하였다.

일반적인 방법의 근관 성형과 세정 그리고 충전을 시행하는데 있어 실험군 들에서는 NaOCl만, NaOCl 과 EDTA, NaOCl과 MTAD를 사용하였고 10일 동안 표준전극과 시편 근관 내에 위치시킨 실험전극 사이의 전기저항을 측정하여 시간에 따른 치근단 누출의 변화를 비교 평가하였다.

실험결과 측정 시간 30분에서 7일 사이에서 smear layer 제거한 군들 (Group 4와 5)에서 제거하지 않은 군 (Group 3)에서 보다 적은 치근단 누출을 보였지만 통계학적인 유의성있는 차이를 나타내지는 않았다. 실험군들 사이에서 모든 시간 대에 걸쳐 치근단 누출의 유의성 있는 차이를 관찰할 수 없었다.

주요어: 도말층 (smear layer), 치근단 누출, 전기화학적 연구, 근관 세정액